



# Synthesis and self-assembly properties of fulleropyrrolidine prepared by Prato reaction

Khanh Hy Le Ho, Stéphane Campidelli

## ► To cite this version:

Khanh Hy Le Ho, Stéphane Campidelli. Synthesis and self-assembly properties of fulleropyrrolidine prepared by Prato reaction. *Advances in Natural Sciences: Nanoscience and Nanotechnology*, 2014, 5 (2), pp.025008. hal-01156571

**HAL Id: hal-01156571**

**<https://hal.science/hal-01156571>**

Submitted on 17 Nov 2015

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## Synthesis and self-assembly properties of fulleropyrrolidine prepared by Prato reaction

This content has been downloaded from IOPscience. Please scroll down to see the full text.

2014 Adv. Nat. Sci: Nanosci. Nanotechnol. 5 025008

(<http://iopscience.iop.org/2043-6262/5/2/025008>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 132.166.48.186

This content was downloaded on 13/06/2014 at 07:01

Please note that [terms and conditions apply](#).

# Synthesis and self-assembly properties of fulleropyrrolidine prepared by Prato reaction

Khanh Hy Le Ho<sup>1</sup> and Stéphane Campidelli<sup>2</sup>

<sup>1</sup> Department of Biochemistry, Institute of Oceanography, Vietnam Academy of Science and Technology, 1 Cau Da, Nha Trang, Khanh Hoa, Vietnam

<sup>2</sup> CEA Saclay, IRAMIS, NIMBE, Laboratory of Innovation in Surface Chemistry and Nanoscience (LICSEN), F-91191 Gif sur Yvette, France

E-mail: [lehokhanhhy@gmail.com](mailto:lehokhanhhy@gmail.com)

Received 13 March 2014

Accepted for publication 1 April 2014

Published 22 April 2014

## Abstract

Molecular self-assembly is considered as a promising way to control the manufacture of new materials and their integration into hybrid devices with novel properties. In this work we have synthesized a fulleropyrrolidine bearing a phenylacetylene moiety via the Prato reaction. The characterization of the fulleropyrrolidine by nuclear magnetic resonance and optical spectroscopy is reported, and its self-assembly by crystallization study has been investigated according to the used solvents. If the solvent that effectively solubilizes fullerene derivative is tetrahydrofuran, the nano-square plates with 1–3  $\mu\text{m}$  in length and 50–100 nm in thickness are formed, while if the solvent is toluene, 5  $\mu\text{m}$  diameter ‘nano-flowers’ are obtained.

Keywords: fullerene, fulleropyrrolidine, self-assembly, nano-square plate, nano-flower

Classification numbers: 4.00, 4.03

## 1. Introduction

During the last fifteen years, fullerene-based supramolecular assemblies have been extensively investigated.  $\text{C}_{60}$  is a highly hydrophobic molecule with a perfect icosahedral symmetry. It also possesses exceptional photophysical properties and low reorganization energy [1]. All these properties make fullerene an ideal candidate for a large number of applications such as solar cells [2, 3], organic light-emitting diode (OLED) [4], organic field-effect transistor (OFET) [5, 6]. The high performance of these optoelectronic devices is often conditioned by supramolecular organized structures of fullerene-based materials. So it is the key to mastering the aspects of supramolecular organization in organic optoelectronic devices.

The first example of fullerene-based supramolecular assemblies was the complexation of  $\text{C}_{60}$  with molecular building blocks that favor the formation of inclusion complexes [7]. Later, by using classical covalent functionalization to make more sophisticated  $\text{C}_{60}$  structures, the size, order, and complexity of the supramolecular assemblies continuously


increased. This method has led to, for example, fullerene-based micelles, vesicles, and aggregates [8–18], polymers [19–25], and liquid crystals [26–35], as well as the organization of fullerene on electrode or nanoparticle surfaces [36–38].

In this paper we explore the self-assembling properties of a fulleropyrrolidine functionalized with a phenylacetylene moiety via the Prato reaction. The characterization of this compound by nuclear magnetic resonance (NMR), optical spectroscopy, x-ray diffraction as well as microscopy allowed identifying the interactions that lead to self-assembly properties.

## 2. Experimental

### 2.1. Material

$\text{C}_{60}$  (99.9%) was purchased from MER Corporation. Chemicals were purchased from Aldrich and were used as received. Solvents were purchased from Aldrich or VWR and

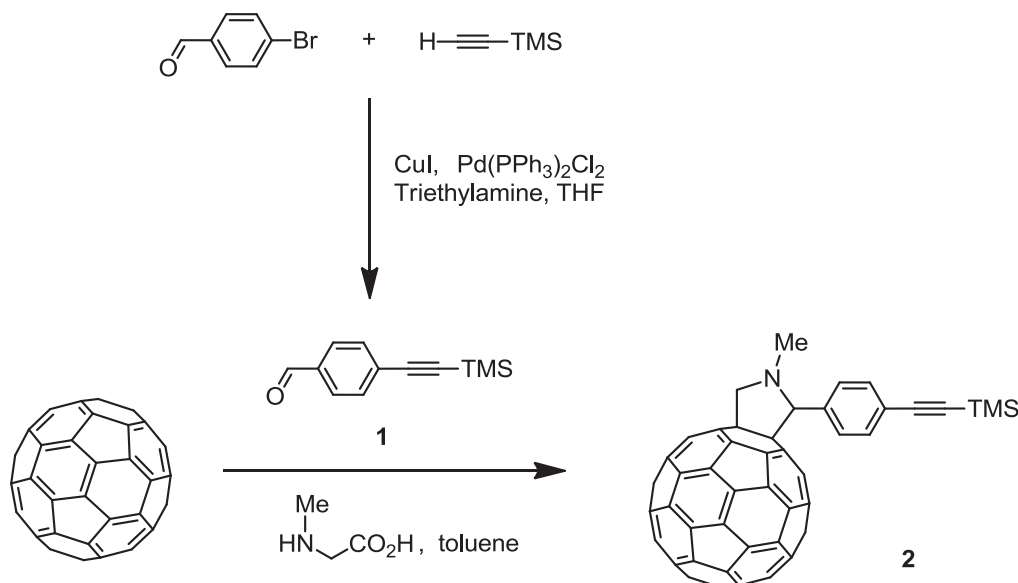

**Scheme 1.** Reagents and conditions of synthesis of fulleropyrrolidine.

were used as-received. For synthesis,  $\text{CH}_2\text{Cl}_2$  ( $\text{CaH}_2$ ,  $\text{N}_2$ ), toluene (K/benzophenone,  $\text{N}_2$ ), tetrahydrofuran (THF) (K/benzophenone,  $\text{N}_2$ ) were distilled before use.

## 2.2. Synthesis of fulleropyrrolidine

The Prato reaction [39] is an example of cycloaddition [3 + 2] from the azomethine ylides which are highly reactive 1,3 dipoles. The ylide is generated *in situ* after decarboxylation of iminium salts obtained by condensation of amino acids and aldehydes. These ylides react with the  $\text{C}_{60}$  to form fulleropyrrolidines. The synthesis of fulleropyrrolidine 2 is described in scheme 1; it is obtained by condensation of 4-(2-trimethylsilylethynyl)benzaldehyde 1 [40] and *N*-methylglycine onto  $\text{C}_{60}$ .

4-(2-trimethylsilylethynyl)benzaldehyde 1 was synthesized by Sonosashira coupling of 4-bromobenzaldehyde and trimethylsilylacetylene: To a stirred mixture of 4-bromobenzaldehyde (9.25 g, 50.0 mmol), CuI (380 mg, 2.0 mmol), and  $\text{Pd}(\text{PPh}_3)_2\text{Cl}_2$  (700 mg, 1.0 mmol) in 50 mL of THF was added triethylamine (10.1 g, 75.0 mmol). A solution of trimethylsilylacetylene (5.15 g, 52.5 mmol) in 10 mL of THF was then added over one hour. The solvent was evaporated, and the residue was treated with pentane. The filtration through Celite and evaporation of the solvent yielded compound 1.

Fulleropyrrolidine 2:  $\text{C}_{60}$  (50 mg, 0.069 mmol) was dissolved in dry toluene 50 mL and then 4-(2-trimethylsilylethynyl)benzaldehyde (14 mg, 0.069 mmol) and *N*-methylglycine (62 mg, 0.693 mmol) were added. The mixture was stirred overnight at reflux, and then evaporated to dryness. The purification of the residue by column chromatography (eluent toluene) and precipitation (dissolution in  $\text{CH}_2\text{Cl}_2$  and precipitation by pouring the solution into MeOH) gave pure 2 as a brown powder.

## 2.3. Techniques

Absorption spectra were recorded in quartz cuvettes on a Perkin–Elmer Lambda 900 UV-Vis-NIR spectrophotometer.  $^1\text{H}$  NMR spectra were recorded with a Bruker ac-300 (300 MHz) spectrometer with solvent used as internal reference; MS (MALDI-TOF) spectra were recorded with a PerseptiveBiosystems Voyager DE-STR spectrometer. Scanning electron microscopy (SEM) measurements were performed using a Hitachi S4500 microscope. Molecular modeling was performed using the HyperChem software in conjunction with the MM+ method.

## 3. Results and discussion

### 3.1. UV-visible absorption spectra

The UV-visible absorption spectra of fulleropyrrolidine 2 in toluene shows two-band characteristics: a narrow and intense peak at 430 nm and a broad band around 700 nm, as shown in figure 1. These peaks are characteristic of fulleropyrrolidine monoadducts [39].

### 3.2. $^1\text{H}$ NMR spectra

Due to the low solubility of compound 2 in  $\text{CDCl}_3$ , the signal-to-noise ratio of the NMR spectrum is not very good, but can be observed in the region between 4–5 ppm three protons belonging to the pyrrolidine (enlarged view of  $^1\text{H}$  NMR spectra shown in 4–5 ppm) (figure 2). We note that the four aromatic protons resonate at 7.50 and 7.73 ppm. The signals of these protons should be doublets any time; because of the presence of the fullerene, they appear as a broad signal. The protons of  $\text{NCH}_3$  resonate at 2.76 ppm and the protons of Si ( $\text{CH}_3$ )<sub>3</sub> at 0.2 ppm.

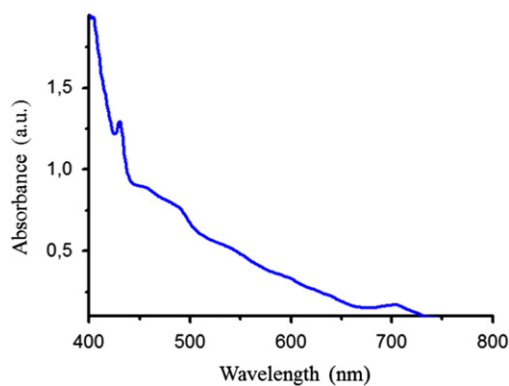


Figure 1. UV-visible spectra of fulleropyrrolidine 2 in toluene.

### 3.3. Self-assembly and SEM photographs

We started by investigating the self-assembly properties of fulleropyrrolidine 2. The sample was dissolved in THF at a concentration of 1 mM, 500  $\mu$ l of this solution was filled into NMR tube and acetonitrile (AcCN) was slowly added to the top of the tube. This tube was capped and the solution was left two days to allow the slow diffusion of AcCN in THF. After two days at room temperature, the formation of precipitate is observed. The suspension was then homogenized and a drop was deposited on a silicon substrate to be imaged by SEM (scheme 2). Figure 3 shows a typical example of the images obtained: nano-square plates with 1–3 micrometers in length and 50–100 nm in thickness.

Nakanishi has extensively studied the different architectural aspects of fullerene self-assembly as a function of the solvents. They showed that very simple molecules can give rise to a wide variety of assemblies according to the solvents used [12]. The difference of organization results from the balance between the ‘good’ and ‘bad’ solvents for fullerene in the mixture. Therefore, we decided to explore the difference between two ‘good’ solvents of the fulleropyrrolidine 2. We solubilized compound 2 in toluene and then AcCN was added. After seven days, the suspension was imaged by SEM, figure 4 shows the type of assemblies obtained: ‘nano-flowers’ with about 5 microns in diameter. It is worth mentioning that toluene is a good solvent for both unfunctionalized fullerene and for compound 2 while THF is able to solubilize only the fulleropyrrolidine derivative. The different interactions of the toluene and THF with the fullerene part of 2 are certainly responsible for the difference of supramolecular organization.

### 3.4. X-ray diffraction and discussion on the formation of precipitate

To understand the organization of molecules in the nano-plates and in the nano-flowers, the precipitates were studied by x-ray diffraction. The diffraction pattern of 2 in the nano-plates (figure 5(a)) shows three reflections,  $d_1 = 21.675$  Å;  $d_2 = 10.77$  Å and  $d_3 = 7.085$  Å. These reflections, with a spacing ratio 1:2:3, indicate a long-range lamellar organization of the  $C_{60}$  moieties with an average lamellar periodicity of


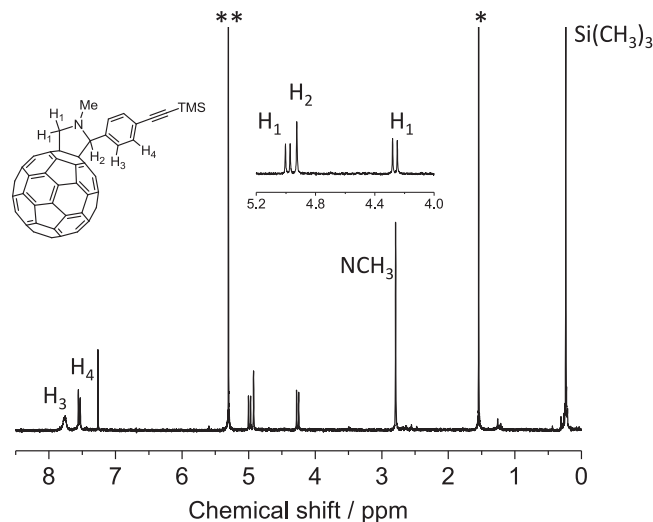


Figure 2.  $^1\text{H}$  NMR Spectra of fulleropyrrolidine 2 in  $\text{CDCl}_3$  (\*\*  $\text{CDCl}_3$ , \*  $\text{H}_2\text{O}$ )  $^1\text{H}$  NMR (300 MHz,  $\text{CDCl}_3$ ):  $\delta = 7.72$  (br, 2H; arom. H), 7.51 (d,  $J = 8.7$  Hz, 2H; arom. H), 4.94 (d,  $J = 9.3$  Hz, 1H; H pyrrolidine), 4.89 (s, 1H; H pyrrolidine), 4.23 (d,  $J = 9.6$  Hz, 1H; H pyrrolidine), 2.76 (s, 3H;  $\text{NCH}_3$ ), 0.20 ppm (s, 9H;  $\text{SiMe}_3$ ); FTIR (KBr):  $\tilde{\nu} = 2948, 2779, 2155, 1500, 1462, 1427, 1331, 1246, 1216, 1122, 1103, 864, 842, 758, 704, 582, 552, 526$   $\text{cm}^{-1}$ ; UV/Vis (toluene):  $\lambda_{\text{max}} = 328, 432, 703$  nm; MS (MALDI-TOF):  $m/z$  calculated for  $\text{C}_{74}\text{H}_{19}\text{NSi}$ : 949.13  $[\text{M-H}]^+$ ; found: 948.13.

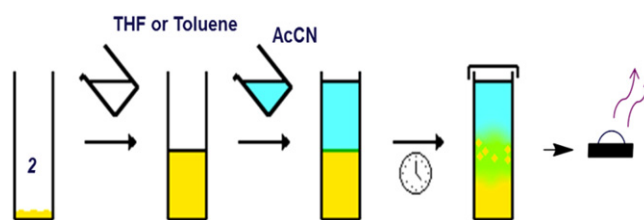


Scheme 2. Crystallization study of fulleropyrrolidine 2.

$d = 21.5$  Å. Other reflections, typically (hkl) with h, k or l indices simultaneously non-zero, reflect three-dimensional extension of the supramolecular nanostructure. In the same way, the diffraction pattern of the nano-flowers shows three reflections,  $d_1 = 24.4$  Å,  $d_2 = 12.18$  Å and  $d_3 = 8.16$  Å (figure 5(b)). These three reflections show once again the lamellar organization of the fulleropyrrolidine in the nanostructures.


By molecular modeling, we estimated that the length of a molecule of 2 is 17.7 Å (figure 6(a)). The interlamellar distance of about 21.5 Å and 24.4 Å in the nano-plates and the nano-flowers, respectively, do not correspond to either the length of a molecule or the length of an interdigitated bilayer of 2 (26.4 Å—figure 6(b)). It is therefore inferred that the molecules are inclined about  $35^\circ$  in the layers of the nano-plates and  $22^\circ$  within the layers of the nano-flowers ( $\cos \alpha = d/26.4$ ) (figure 6(c)).

‘Nano-flowers’ assemblies have been obtained by Nakanishi *et al* by slow cooling of a solution of fulleropyrrolidine containing long alkyl chains in 1,4-dioxane at  $60^\circ\text{C}$  to  $5^\circ\text{C}$  [41]. They explained the formation of these



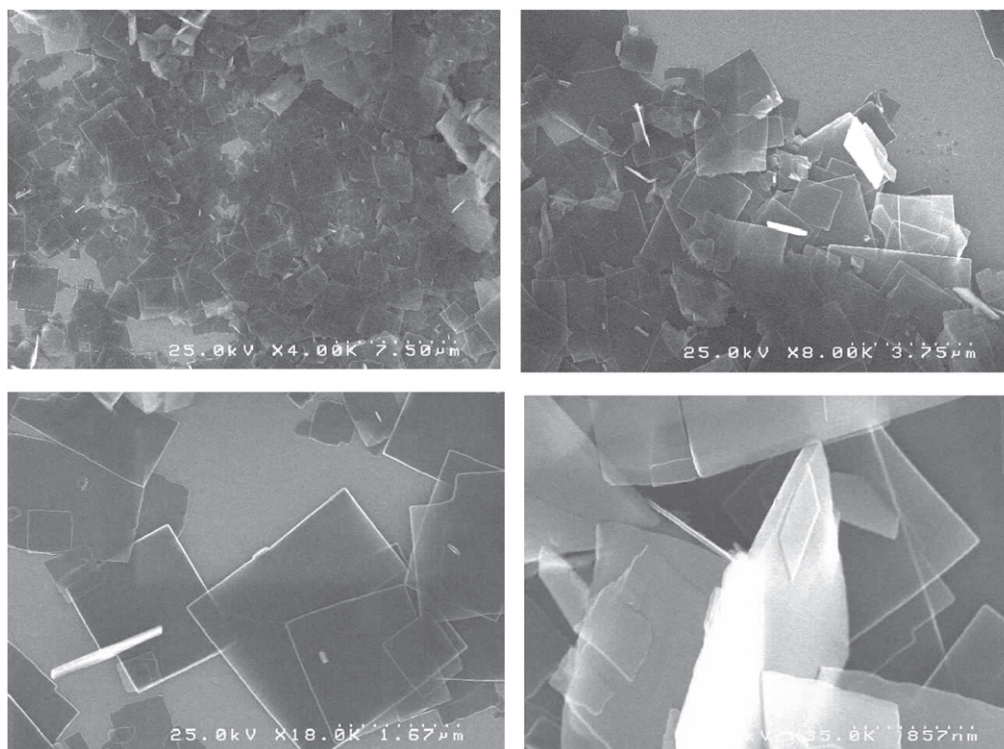

**Figure 3.** SEM images of nano-plates obtained by self-assembly of fulleropyrrolidine 2 in the mixture of THF/AcCN.

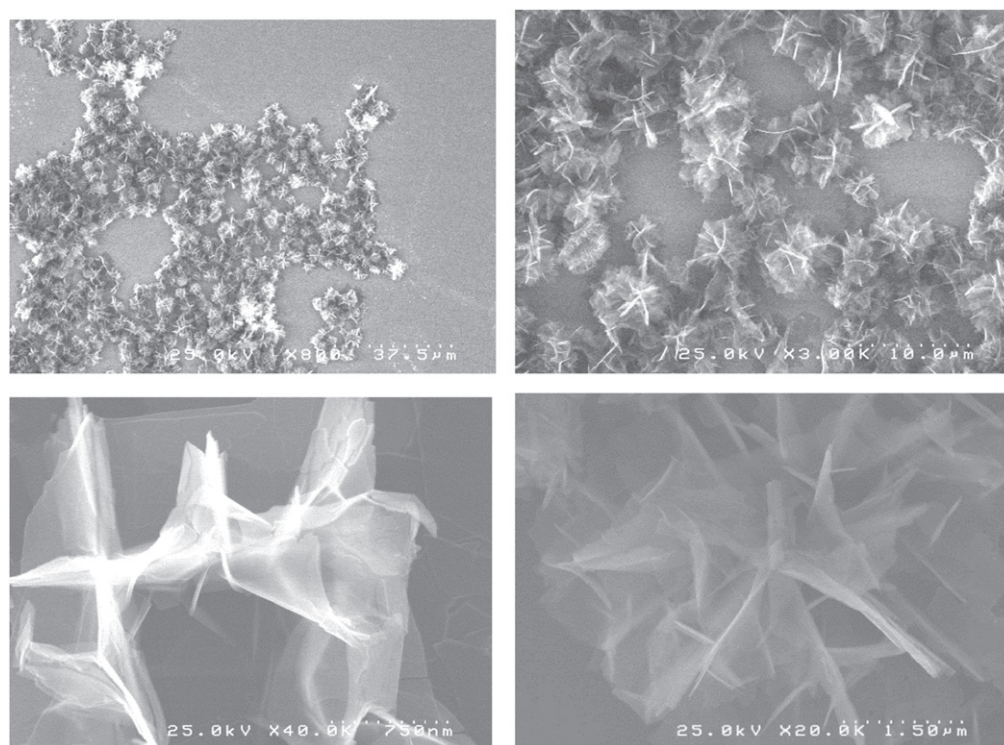


**Figure 4.** SEM images of nano-flowers obtained by self-assembly of fulleropyrrolidine 2 in the mixture of toluene/AcCN.


objects by the successive folding of a very thin film of molecules.

#### 4. Conclusion

We have described herein the synthesis and characterization of fulleropyrrolidine monoadduct bearing a phenyl-trimethylsilylacetylene moiety formed by Prato reaction. The

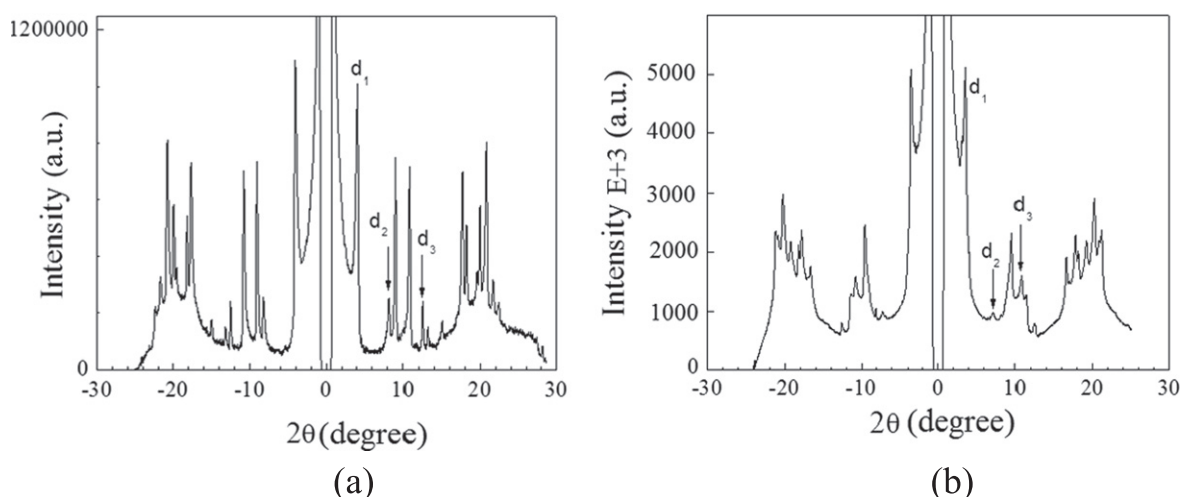

**Figure 5.** Small-angle x-ray diffractogram of the nano-plates (a) and the nano-flowers (b) formed by fulleropyrrolidine 2.

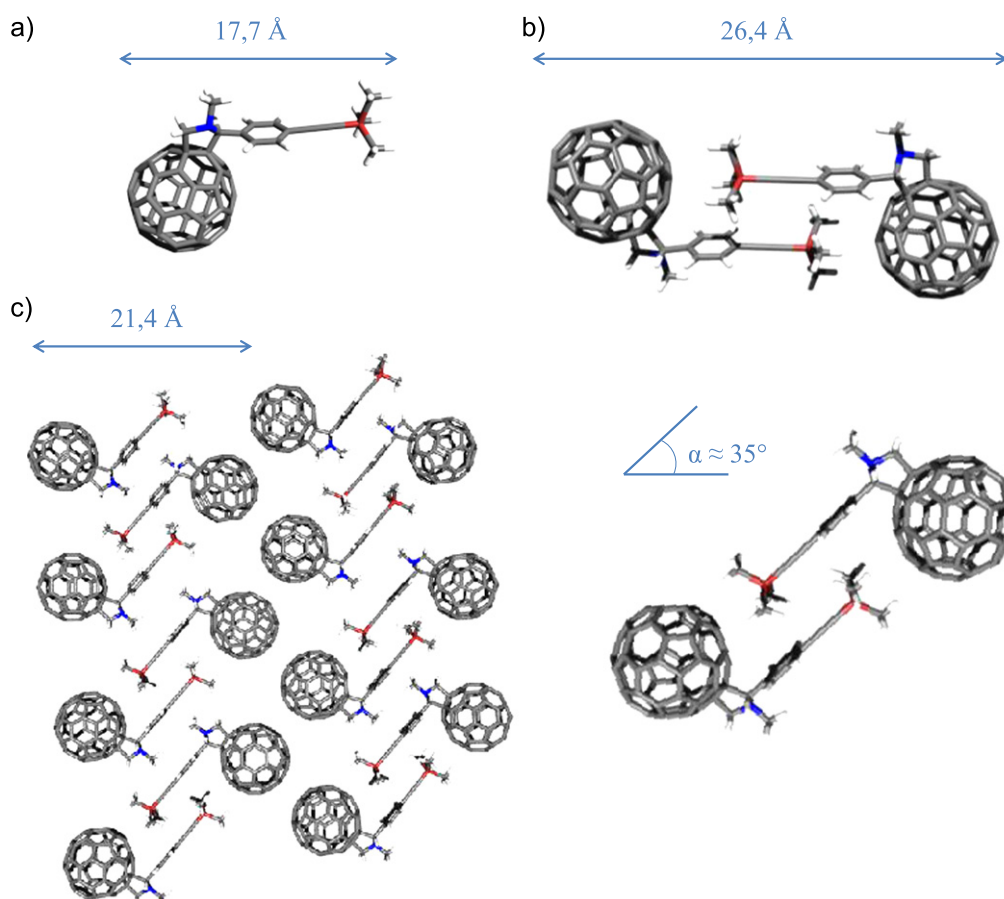

**Figure 6.** Estimated length of 2 (a) and an interdigitated bilayer of 2 (b); representation of the organization of 2 in the bilayers of nano-plates (c).

self-assembly properties of the fulleropyrrolidine derivative have been investigated. The formation of the nano-plates and 'nano-flowers' seem more dependent on the interactions of the molecules with the solvent than the interactions between molecules themselves. Indeed, the organization is governed by the careful balance between 'good' and 'bad' solvents for the fullerene derivatives.

### Acknowledgment

This work has been partially supported by ANR (project f-DNA ANR-09-NANO-005-01). The authors warmly thank Benoit Heinrich and Dr Bertrand Donnio from the IPCMS in Strasbourg (France) for performing small-angle x-ray diffraction experiments.

## References

- [1] Guldi D M 2002 *Chem. Soc. Rev.* **31** 22
- [2] Hoppe H and Sariciftci N S 2006 *J. Mater. Chem.* **16** 45
- [3] Dang M T, Hirsch L, Wantz G and Wuest J D 2013 *Chem. Rev.* **113** 3734
- [4] Lee J Y and Kwon J H 2005 *Appl. Phys. Lett.* **86** 63514
- [5] Haddock J N, Zhang X, Domercq B and Kippelen B 2005 *Organics Electronics* **6** 182
- [6] Li H, Tee B C-K, Judy J C, Yi C, Jong W C, Sang Y L and Bao Z 2012 *J. Am. Chem. Soc.* **134** 2760
- [7] Diederich F and Gmez-Lpez M 1999 *Chem. Soc. Rev.* **28** 263
- [8] Burghardt S, Hirsch A, Schade B, Ludwig K and Bçttcher C 2005 *Angew. Chem.* **117** 3036
- [8] Burghardt S, Hirsch A, Schade B, Ludwig K and Bçttcher C 2005 *Angew. Chem. Int. Ed.* **44** 2976
- [9] Zhou S, Burger C, Chu B, Sawamura M, Nagahama N, Toganoh M, Hackler U E, Isobe H and Nakamura E 2001 *Science* **291** 1944
- [10] Nakashima N, Ishii T, Shirakusa M, Nakanishi T, Murakami H and Sagara T 2001 *Chem. Eur. J.* **7** 1766
- [11] Nakanishi T, Schmitt W, Michinobu T, Kurth D G and Ariga K 2005 *Chem. Commun.* 5982
- [12] Nakanishi T 2010 *Chem. Commun.* **46** 3425
- [13] Cassell A M, Asplund C L and Tour J M 1999 *Angew. Chem.* **111** 2565
- [13] Cassell A M, Asplund C L and Tour J M 1999 *Angew. Chem. Int. Ed.* **38** 2403
- [14] Georgakilas V, Pellarini F, Prato M, Guldi D M, Melle-Franco M and Zerbetto F 2002 *Proc. Natl. Acad. Sci. USA* **99** 5075
- [15] Hizume Y, Tashiro K, Charvet R, Yamamoto Y, Saeki A, Seki S and Aida T 2010 *J. Am. Chem. Soc.* **132** 6628
- [16] Charvet R, Yamamoto Y, Sasaki T, Kim J, Kato K, Takata M, Saeki A and Aida T 2012 *J. Am. Chem. Soc.* **134** 2524
- [17] Babu S S, Moehwald H and Nakanishi T 2010 *Chem. Soc. Rev.* **39** 4021
- [18] Le Ho K H *et al* 2013 *Chem. Eur. J.* **19** 11374
- [19] Giacalone F and Martín N 2006 *Chem. Rev.* **106** 5136
- [20] Fernández G, Pérez E M, Sánchez L and Martín N 2008 *Angew. Chem. Int. Ed.* **47** 1094
- [21] Fernández G, Pérez E M, Sánchez L and Martín N 2008 *J. Am. Chem. Soc.* **130** 2410
- [22] Nishimura T, Tsuchiya K, Ohsawa S, Maeda K, Yashima E, Nakamura Y and Nishimura J 2004 *J. Am. Chem. Soc.* **126** 11711
- [23] Haino T, Hirai E, Fujiwara Y and Kashihara K 2010 *Angew. Chem.* **122** 8071
- [23] Haino T, Hirai E, Fujiwara Y and Kashihara K 2010 *Angew. Chem. Int. Ed.* **49** 7899
- [24] Wang C-L *et al* 2011 *Adv. Mater.* **23** 2951
- [25] Wang C-L, Zhang W-B, Sun H-J, Van Horn R M, Kulkarni R R, Tsai C-C, Hsu C-S, Lotz B, Gong X and Cheng S Z D 2012 *Adv. Energy Mater.* **2** 1375
- [26] Deschenaux R, Donnio B and Guillon D 2007 *New J. Chem.* **31** 1064
- [27] Lenoble J, Campidelli S, Maringa N, Donnio B, Guillon D, Yevlampieva N and Deschenaux R 2007 *J. Am. Chem. Soc.* **129** 9941
- [28] Maringa N, Lenoble J, Donnio B, Guillon D and Deschenaux R 2008 *J. Mater. Chem.* **18** 1524
- [29] Campidelli S, Bourgun P, Guintchin B, Furrer J, Stoeckli-Evans H, Saez I M, Goodby J W and Deschenaux R 2010 *J. Am. Chem. Soc.* **132** 3574
- [30] Hoang T N Y, Pocięcha D, Salamoneczyk M, Gorecka E and Deschenaux R 2011 *Soft Matter* **7** 4948
- [31] Mamlouk H, Heinrich B, Bourgogne C, Donnio B, Guillon D and Felder-Flesch D 2007 *J. Mater. Chem.* **17** 2199
- [32] Vergara J, Barberá J, Serrano J L, Ros M B, Sebastián N, de La Fuente R, López D O, Fernández G, Sánchez L and Martín N 2011 *Angew. Chem.* **123** 12731
- [32] Vergara J, Barberá J, Serrano J L, Ros M B, Sebastián N, de La Fuente R, López D O, Fernández G, Sánchez L and Martín N 2011 *Angew. Chem. Int. Ed.* **50** 12523
- [33] Sawamura M, Kawai K, Matsuo Y, Kanie K, Kato T and Nakamura E 2002 *Nature* **419** 702
- [34] Matsuo Y, Muramatsu A, Hamasaki R, Mizoshita N, Kato T and Nakamura E 2004 *J. Am. Chem. Soc.* **126** 432
- [35] Matsuo Y, Muramatsu A, Kamikawa Y, Kato T and Nakamura E 2006 *J. Am. Chem. Soc.* **128** 9586
- [36] Imahori H 2007 *Bull. Chem. Soc. Jpn.* **80** 621
- [37] Imahori H 2007 *J. Mater. Chem.* **17** 31
- [38] Bonifazi D, Enger O and Diederich F 2007 *Chem. Soc. Rev.* **36** 390
- [39] Maggini M, Scorrano G and Prato M 1993 *J. Am. Chem. Soc.* **115** 9798
- [39] Prato M and Maggini M 1998 *Acc. Chem. Res.* **31** 519
- [40] Thorand S and Krause N 1998 *J. Org. Chem.* **63** 8551
- [41] Nakanishi T, Ariga K, Michinobu T, Yoshida K, Takahashi H, Teranishi T, Mçhwald H and Kurth D G 2007 *Small* **3** 2019